

## FRACTURE ASSESSMENT DIAGRAM FOR SOLID WITH CIRCULAR CRACK SUBJECTED TO CONCENTRATED FORCES

V.I. Smirnov

Petersburg State Transport University, St.-Petersburg, Russia

e-mail: vsmirnov1@gmail.com

**Abstract.** Structural criterion of fracture is used to evaluate the ultimate load for solid weakened by circular crack deformed by the action of two point forces applied to the crack faces at its center. Estimation of the risk of failure is based on the two-criterion approach under linear elastic conditions.

It is known that the widely used classical criteria of fracture suggested by Griffith and Irwin do not applicable for short unstable cracks as they lead to unlimited critical load. To overcome this difficulty the structural strength criterion was proposed. For the penny shaped crack embedded in an infinite solid and subjected to axisymmetric loading conditions this criterion is expressed as [1]

$$\frac{2}{2ad + d^2} \int_a^{a+d} \sigma_z(r)r dr \leq \sigma_c, \quad (1)$$

where  $a$  – crack radius,  $(r, z)$  – cylindrical coordinates,  $\sigma_c$  – tensile strength limit,  $d$  – structural fracture parameter of the dimension of length, so called fracture process zone,  $\sigma_z$  – normal stress at the plane  $z = 0$ ,  $r > a$ .

General solution for the tensile stress ahead of the crack is given in [2, 3]

$$\sigma_z(r, 0) = \frac{2}{\pi\sqrt{r^2 - a^2}} \int_0^a \frac{\rho\sqrt{a^2 - \rho^2}}{r^2 - \rho^2} p(\rho) d\rho. \quad (2)$$

The pressure on crack faces is given by

$$p(\rho) = \frac{P}{2\pi\rho} \delta(\rho), \quad (3)$$

where  $P$  – concentrated force,  $\delta(\rho)$  – Dirac delta-function. Substituting for  $p(\rho)$  from equation (3) into equation (2), we obtain

$$\sigma_z(r, 0) = \frac{Pa}{\pi^2 r^2 \sqrt{r^2 - a^2}}, \quad r > a.$$

Substituting into (1) and evaluating the integral, we find (Fig.1, curve 1)

$$\frac{p_*}{\sigma_c} = \frac{\pi(1+\eta)}{2(1-\eta)\arccos\eta}, \quad 0 \leq \eta \leq 1, \quad (4)$$

where  $\eta = a / (a + d)$  – dimensionless crack radius,  $p_*$  – critical load (stress)  $p_* = P_* / (\pi d^2)$ . As  $\eta \rightarrow 0$  (infinitely small crack) we have physically unaffected limit




$$\frac{\partial}{\partial a}(W + U) = 0, \quad (7)$$

where  $W$  – potential energy supplied by the internal strain energy and external forces,  $U$  – work required to create new surfaces. The potential energy is given by [8]

$$W = \frac{2\pi^2(1-\nu^2)}{E} \int_0^a [g(t)]^2 dt, \quad g(t) = \frac{2}{\pi} \int_0^t \frac{rp(r)}{\sqrt{t^2-r^2}} dr.$$

where  $\nu$  – Poisson's ratio,  $E$  – elasticity modulus.

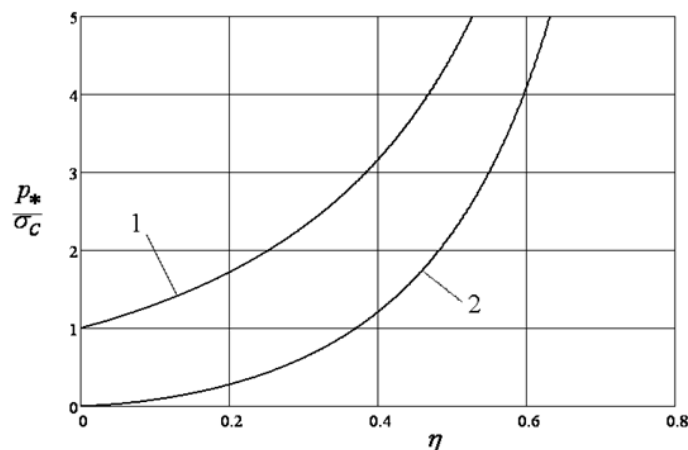

**Fig. 2.** Critical load versus crack size:  
1 – structural criterion (4), 2 – Irwin criterion (6).

For the load (3) we have  $g(t) = P / (\pi^2 t)$ . Thus,

$$W = \frac{2(1-\nu^2)P^2}{\pi^2 Ea}.$$

Since the formation of a crack requires the creation of two surfaces  $U$  becomes

$$U = 2\gamma \cdot \pi a^2,$$

where  $\gamma$  is the surface energy of the material.

From the equation (7) we deduce critical force according to Griffith criterion

$$P_* = \sqrt{\frac{2\gamma E}{1-\nu^2}} (\pi a)^{3/2}. \quad (8)$$

Fracture toughness is related to constant  $\gamma$  by equation  $K_{Ic} = \sqrt{2\gamma E / (1-\nu^2)}$ , implying the similarity between Griffith and Irwin approaches in linear fracture mechanics (plain strain).

Equation (8) may be expressed as  $P_* = K_{Ic} (\pi a)^{3/2}$ , which immediately follows from the Irwin criterion.

On recalling the plain strain analogy the critical load may be put in the form [9]

$$P_* = \sqrt{\frac{2\gamma E}{1-\nu^2}} \pi l, \quad (9)$$

where  $2l$  is length of the crack and the plate thickness is set equal to unity.

It follows from (8) and (9) that critical force tends to zero as  $a, l \rightarrow 0$ . (It should be noted, that in experiments with glass samples equation (9) has been used for the cracks with a

minimal length of  $2l \sim 5 \text{ cm}$  [9]). Structural criterion does give the finite value of critical load as  $a \rightarrow 0$ :  $P_* = \sigma_c \cdot \pi d^2$ . The latter result is in agreement with the tensile strength of intact medium.

### References

- [1] V.I. Smirnov // *Journal of Applied Mechanics and Technical Physics* **48** (2007) 605.
- [2] V.V. Panasyuk, *Limiting equilibrium of brittle solids with fracture* (Michigan Inform. Serv., Detroit, 1971).
- [3] L.I. Slepyan, *Mechanics of Cracks* (Sudostroenie, Leningrad, 1990).
- [4] Yu. Petrov, V.V. Taraban // *Vestnik of St. Petersburg University: Mathematics. Mechanics. Astronomy* (1999) 101. (In Russian).
- [5] K. Ando, B.A. Kim, M. Iwasa, N. Ogura // *Fatigue and Fracture of Engineering Materials and Structures* **15** (1992) 139.
- [6] A.R. Dowling, C.H.A. Townley // *International Journal of Pressure Vessels and Piping* **3** (1975) 77.
- [7] R.P. Harrison, In: *Fracture Mechanics in Engineering Practice*, ed. by P. Stanely. (Applied Science Publishers Ltd., London, 1977), p. 69.
- [8] I.N. Sneddon // *Proceedings of Cambridge Philosophical Society* **61** (1965) 609.
- [9] V.V. Panasyuk, S.E. Kovchik // *Doklady Physics* **146** (1962) 82. (In Russian).