

# MODELING OF ELASTOPLASTIC STEEL DEFORMATION IN TWO-LINK BROKEN TRAJECTORIES AND DELAYING OF VECTOR AND SCALAR MATERIAL PROPERTIES

V.G. Zubchaninov<sup>1</sup>, E.G. Alekseeva<sup>2</sup>, A.A. Alekseev<sup>1\*</sup>, V.I. Gultiaev<sup>1</sup>

<sup>1</sup>Tver State Technical University, nab. Afanasiya Nikitina, 22, Tver, 170026, Russia

<sup>2</sup>Bauman Moscow State Technical University, ul. Baumanskaya 2-ya, 5/1, Moscow, 105005, Russia

\*e-mail: alexeev@bk.ru

**Abstract.** On the basis of a mathematical model of A. A. Il'yushin's theory of elastoplastic processes, numeric calculations are given for programs of experiments in the form of two-link broken strain trajectory. The results of the numeric simulation are compared with the experimental data obtained by authors on the automated test-machine SN-EVM. Delaying of vector and scalar properties is investigated. The instability of magnitude of the trace of delay as a characteristic of the material is shown.

**Keywords:** plasticity; complex loading; two-link trajectories; loading process; vector and scalar properties; trace of delay

## 1. Introduction

The theory of constitutive relations is one of the important directions in the mechanics of deformable solids. It was formed due to the experimental and theoretical development of the theory of plasticity. The solution of elastoplastic boundary value problems, which are based on physically nonlinear constitutive relations, designed to reliably describe the properties of materials in a wide variety of operating conditions, is not easy for theoretical analysis. For verification of the physical integrity of the constitutive relations of the theory of plasticity, it is necessary to carry out calculations and compare the obtained numerical results with experimental data on a wide class the trajectories of deformation. The main mathematical models of the theory of plasticity and the results of numerous experiments with complex loading of materials are partially presented in [1-11] and others.

In this paper, to verify the mathematical model of elastoplastic processes theory, calculations of the deformation processes of steel 45 are carried out on two-link broken trajectories (tension with torsion; P–M tests). The results of numeric simulation are compared with the experimental data obtained by the authors on the automated test-machine SN-EVM. Previously, variants of the mathematical model showed good agreement with experimental data on two-link strain trajectories containing curved sections, both in the presence and absence of break points [12-14].

Experimental test procedure is based on the theory of elastoplastic processes by A.A. Il'yushin [1,2], in which stress and strain variation history with the course of time is represented by the corresponding trajectories in the five-dimensional vector spaces. In this case, the bonding between stress and strains is described as scalar properties characterizing the bonding between invariants of stress and strain deviators, and vector properties characterizing the disalignment of stress and strains deviators, and their increments.

Il'yushin further proposed the principle of delay [2], which states that the stress response to a strain trajectory is not defined by the whole strain trajectory, but by the recent past known as the trace of delay of the vector properties of the material  $\lambda$ . Studies of the value  $\lambda$  under complex loading are devoted to the work [3,15-18] in which the instability  $\lambda$  is noted. This paper also shows the instability of the trace of delay of the scalar properties of the material  $\lambda_{sc}$ .

## 2. Main equations

In a linear combined space  $E_6$  of stresses and strains with an orthonormal basis  $\{\hat{i}_k\}$  for stress  $\sigma_{ij}$  and strain  $\varepsilon_{ij}$  tensors

$$\sigma_{ij} = \sigma_0 \delta_{ij} + S_{ij}, \quad \sigma_0 = \sigma_{ij} \delta_{ij} / 3, \quad \varepsilon_{ij} = \varepsilon_0 \delta_{ij} + \mathcal{E}_{ij}, \quad \varepsilon_0 = \varepsilon_{ij} \delta_{ij} / 3 \quad (1)$$

vectors are assigned

$$\bar{S} = S_0 \hat{i}_0 + \bar{\sigma}, \quad \bar{\sigma} = S_k \hat{i}_k, \quad \bar{\varepsilon} = \mathcal{E}_0 \hat{i}_0 + \bar{\mathcal{E}}, \quad \bar{\mathcal{E}} = \mathcal{E}_k \hat{i}_k, \quad (k = 1, 2, \dots, 5), \quad (2)$$

where vectors coordinates  $S_k$ ,  $\mathcal{E}_k$  related to tensor  $\sigma_{ij}$ ,  $\varepsilon_{ij}$  and deviator components  $S_{ij}$ ,  $\mathcal{E}_{ij}$  noted by unequivocal transformation [1,2]. The volume strain in  $E_6$  is assumed to be elastic according to the law  $\sigma_0 = 3K\varepsilon_0$ , where  $K$  is modulus of volume elasticity (Bulk modulus).

According A.A. Il'yushin's isotropy postulate [1], stress  $\bar{\sigma}$  and strain  $\bar{\mathcal{E}}$  vectors are bound by constitutive relations, which for a planar rectilinear trajectories are:

$$\frac{d\bar{\sigma}}{ds} = M_1 \frac{d\bar{\mathcal{E}}}{ds} + \left( \frac{d\sigma}{ds} - M_1 \cos \vartheta_1 \right) \frac{\bar{\sigma}}{\sigma}, \quad \frac{d\vartheta_1}{ds} = -\frac{M_1}{\sigma} \sin \vartheta_1, \quad (3)$$

where  $M_1$ ,  $\frac{d\sigma}{ds}$  – functionals, depending on the following parameters of complex loading:  $s$

– the arc length of the trajectories of strain and its break angle  $\vartheta_1^0$ . The angle of delay  $\vartheta_1$  characterizes the direction of the vector  $\bar{\sigma}$  towards the shearing to strain trajectory at each point. This angle reflects the influence of the vector properties of the material on the deformation process.

In the mathematical model of materials plastic deformation process theory in addition to the equations (3) uses universal approximations of functionals proposed by V.G. Zubchaninov [3]

$$\sigma(s) = \Phi(s) - Af^p \left( \vartheta_1^0 \right) \Omega(\Delta s), \quad M_1 = 2G_p + (2G - 2G_p^0) f^q, \quad (4)$$

where  $\Phi(s)$  – universal function of Odkvist-Il'yushin for simple (proportional) loading;  $G$ ,  $G_p$  – elastic and secant shear modulus;  $\Delta s = s - s_K^T$ ;  $s_K^T$  – arc length at the break point K of trajectory;


$$f = \frac{1 - \cos \vartheta_1}{2}, \quad \Omega(\Delta s) = \gamma \Delta s e^{-\gamma \Delta s} + b \left( 1 - e^{-\gamma \Delta s} \right) \quad (5)$$

– complex loading function;  $A$ ,  $b$ ,  $\gamma$ ,  $p$ ,  $q$  – observed approximation parameters [3]. The index «zero» refers to the quantities at the break point of trajectory. The numerical solution of the defining relations (3) for the acquainted functionals (4) is implemented by the Runge-Kutta method of the fourth order of accuracy using the MathWorks Matlab software package. The strain vector trajectory is specified and the stress vector trajectory is obtained by integrating equations.


### 3. Comparison of numerical results with experimental ones

Using the foregoing mathematical model, experimental studies and numerical calculations of the processes of deformation of thin-walled tubular specimens of steel 45 on the SN-EVM testing complex along two-link broken strain trajectory in the plane  $\vartheta_1 - \vartheta_3$ , producing a plane state of stress in the wall of the tube. Specimens on the first link were twisted to a value  $\vartheta_3^0 = 2\%$  and on the second link had been tested under combined tension and torsion.


Figures 1-4 show the results of calculations and experimental data for two-link strain trajectory with the break angle  $45^\circ$ . The experimental data are marked with circles. Figure 1 shows the implemented strain trajectory in the plane  $\vartheta_1 - \vartheta_3$ , and on Fig. 2 the response to it in the stress space on the plane  $S_1 - S_3$  is described. Figure 3 the diagram of tracing the straining process  $\sigma - s$ , characterizing the scalar properties of the material is presented, and on Fig. 4 chart  $\vartheta_1 - \Delta s$  characterizing vector properties of the material.

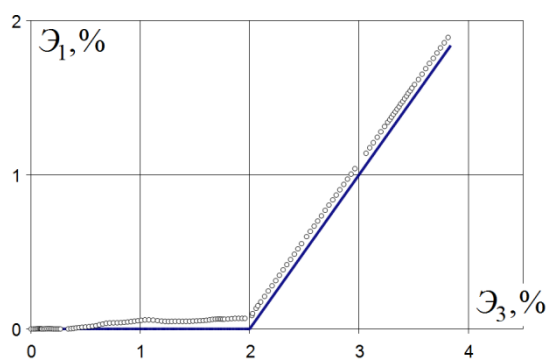


**Fig. 1.** Strain trajectory with the break angle  $45^\circ$

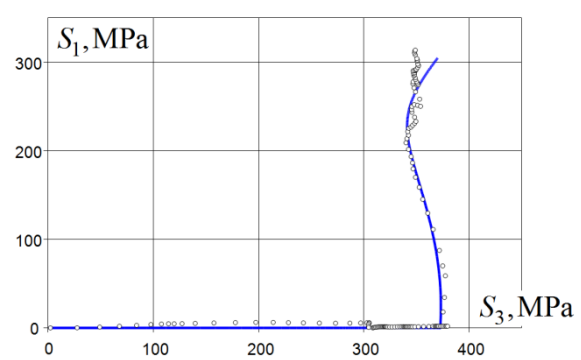

**Fig. 2.** The response  $S_1 - S_3$

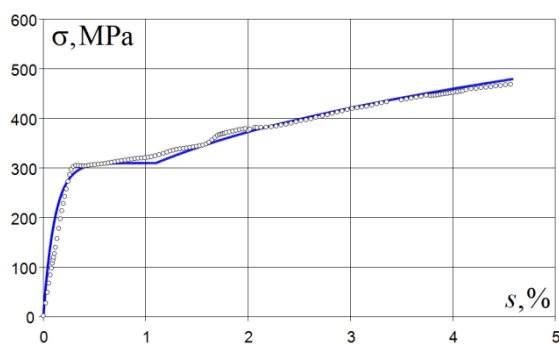


**Fig. 3.** Chart of deformation  $\sigma - s$

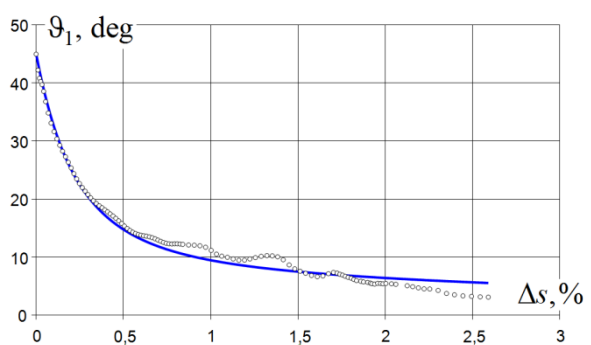


**Fig. 4.** Chart  $\vartheta_1 - \Delta s$


Figures 5-8 present the results of calculation and experimental data for two-link strain trajectory with the break angle  $90^\circ$  and Fig. 9-12 – with the break angle  $135^\circ$ .

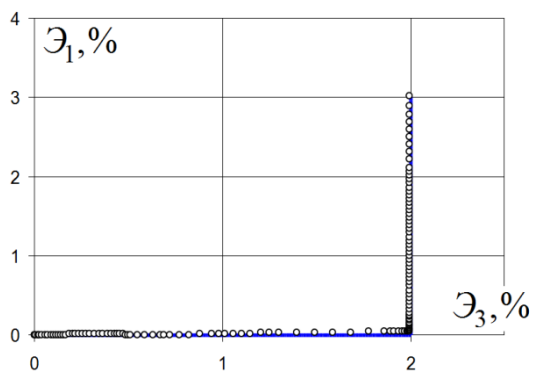


**Fig. 5.** Strain trajectory with the break angle  $90^\circ$

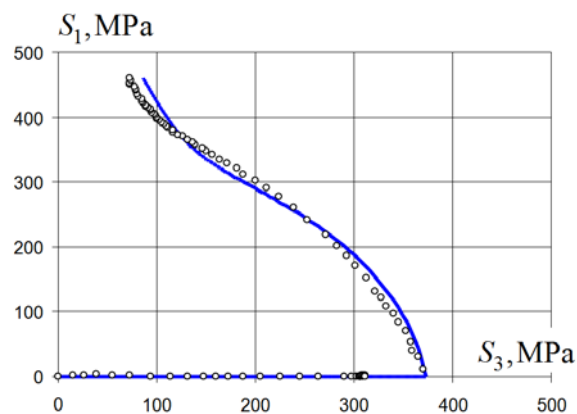


**Fig. 6.** The response  $S_1 - S_3$

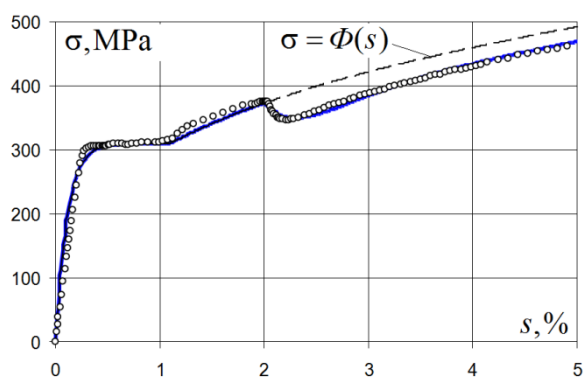


**Fig. 7.** Chart of deformation  $\sigma - s$

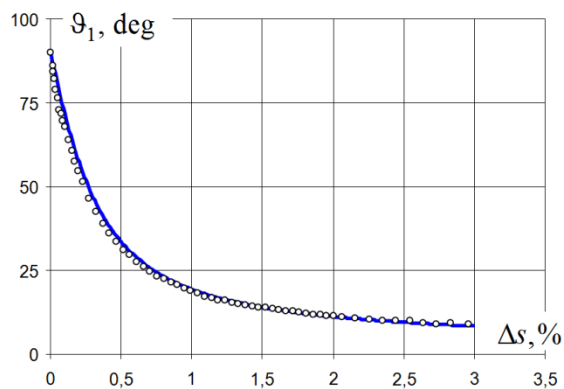


**Fig. 8.** Chart  $\vartheta_1 - \Delta s$

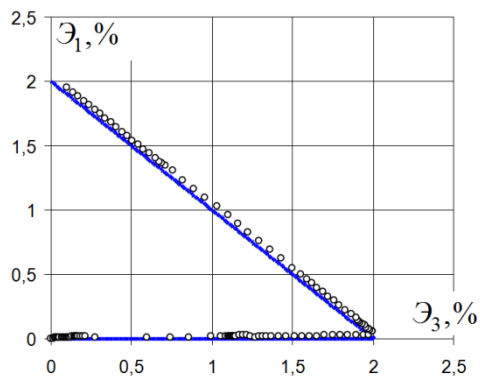


**Fig. 9.** Strain trajectory with the break angle  $135^\circ$

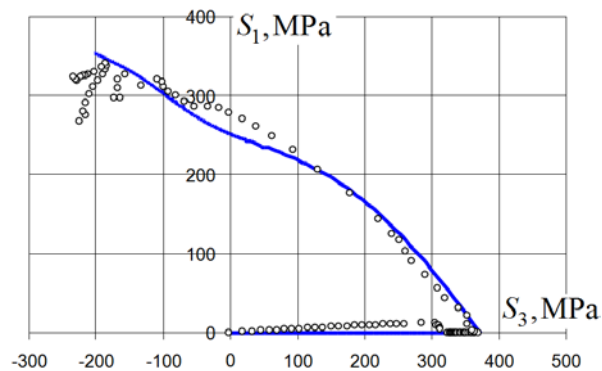

**Fig. 10.** The response  $S_1 - S_3$

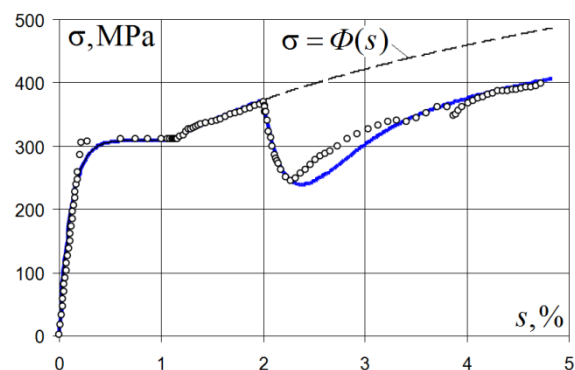

**Fig. 11.** Chart of deformation  $\sigma - s$

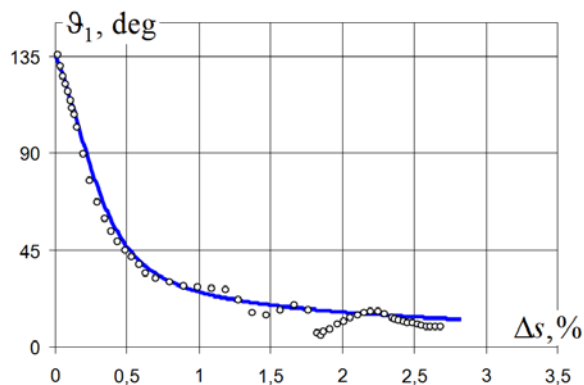

**Fig. 12.** Chart  $\theta_1 - \Delta s$


As we can see, the numerical calculations according to the mathematical model are in good agreement with the experimental data on scalar and vector properties, both qualitatively and quantitatively. This shows the integrity of the calculated data, sufficient for practical problems and the acceptable accuracy of the constructed approximations of the functional processes in the mathematical model of the processes theory applied to this class of trajectories. The modified version of the model has been successful at multi-link broken trajectories [19].

#### 4. The property of delay vector and scalar characteristics of the materials


In [4] A.A. Ilyushin noted that the delay of vector properties is a common property of all plastic materials. The experiments show that the direction of the stress vector at some point K relative to the strain trajectory does not depend on the entire previous path, but only on its limited part, called the trace of delay  $\lambda$ . Usually, the trace of delay  $\lambda$  is determined on two-link broken trajectories at different break angles of the trajectory  $\theta_1^0$  [2,3,15,20-22].

By hypothesis of R.A. Vasin, it is considered [15] that the trace of delay is exhausted when the angle of delay  $6^\circ \div 7^\circ$  is achieved, which is equivalent to the Hencky-II'yushin theory of small elastic-plastic deformations. The magnitude estimation of the trace of delay of the vector characteristics of the material  $\lambda$  from the break angle of the trajectory  $\theta_1^0$  could not be carried out, according to the experimental data in the realized experiments, because the specimens were destroyed before the angle of delay achieved  $\theta_1^* \approx 7^\circ$ , so the evaluation is made according to the calculated data of the model, which is well within the experiments.

Figure 13 shows the combined dependency graphs  $\theta_1 - \Delta s$  for the implemented two-link strain trajectories, and on Fig. 14 the calculated dependence of the trace of delay of the vector characteristics of the material  $\lambda$  on the break angle of the trajectory is given. As you can see, the trace of delay  $\lambda$  significantly depends on the break angle of the trajectory  $\theta_1^0$ , which is indicative of the complexity of the process. This instability means that the trace of delay  $\lambda$  cannot be taken as a constant characteristic of the material.

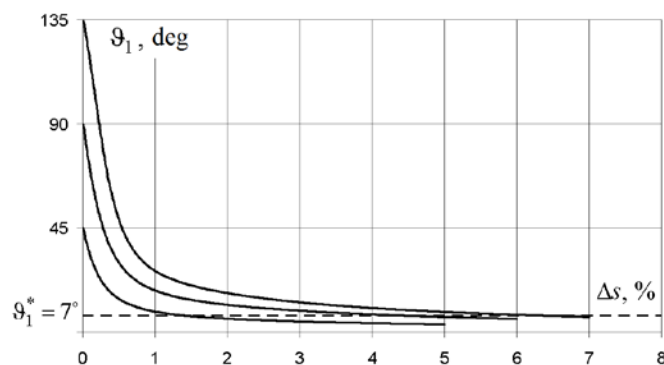

**Fig. 13.** Chart  $\vartheta_1 - \Delta s$  for different break angles of trajectories

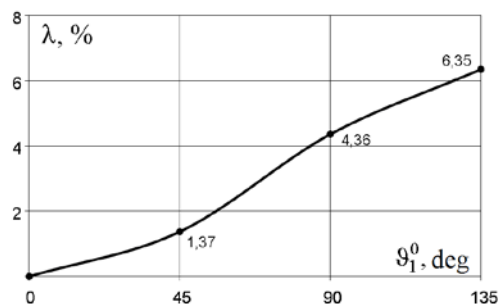


**Fig. 14.** Chart  $\lambda - \vartheta_1^0$

If we divide the current value of the angle of delay  $\vartheta_1$  by the value of the angle of delay at the break point of trajectory  $\vartheta_1^0$ , we get a relative angle of delay  $\tilde{\vartheta}_1 = \vartheta_1 / \vartheta_1^0$ . However, it is impossible to postpone the value  $\vartheta_1^* = 6^\circ - 7^\circ$  on the axis with a dimensionless quantity. In [20] proposed to consider the trace of delay  $\lambda$  exhausted when the  $\vartheta_1^0$  decreases by 15 times. In dimensionless quantities to determine the trace of delay, we can take the value of the angle of delay equal to  $1/15 \approx 0,067$ . When  $\vartheta_1^0 = 90^\circ$  this corresponds to the value  $\vartheta_1^* = 6^\circ$ , i.e. accuracy Hencky-II'yushin theory.


Figure 15 shows the dependence of the relative angle of delay  $\tilde{\vartheta}_1$  on the increment of the arc length of the strain trajectory after a break. It can be seen that for all the break angles, the calculated charts practically coincide with each other. Thus, it is fair to assumed that the dependence of the relative angle of delay  $\tilde{\vartheta}_1$  on the increment of the arc length of the trajectory of deformation after the break  $\Delta s$  is universal and does not depend on the break angle of the trajectory (for the same length of the first link of strain trajectory)

V.S. Lensky in his work [23] introduced the concept of trace of delay of the scalar properties of materials. Fig. 16 shows the dependence on the break angle of the trajectory for the scalar trace of delay of material  $\lambda_{sc}$ . For the value  $\lambda_{sc}$  on the diagram  $\sigma - s$  was equal to the distance along the arc length from the break point of trajectory with the value  $\sigma_k^T$  to the point at which the stress after the «dive» again achieved significance  $\sigma_k^T$ .

This dependence (Fig. 16) shows that the characteristic  $\lambda_{sc}$  is also unstable, and when compared with Fig. 14, it is seen that  $\lambda_{sc} \neq \lambda$ , while the trace of delay of vector characteristics  $\lambda$  was several times larger than the trace of delay of the scalar characteristics  $\lambda_{sc}$ . In the future, the graphs (Figs. 14, 16) can be used to determine the values of the parameters of approximations of the process functionals responsible for the vector and scalar properties of the materials.

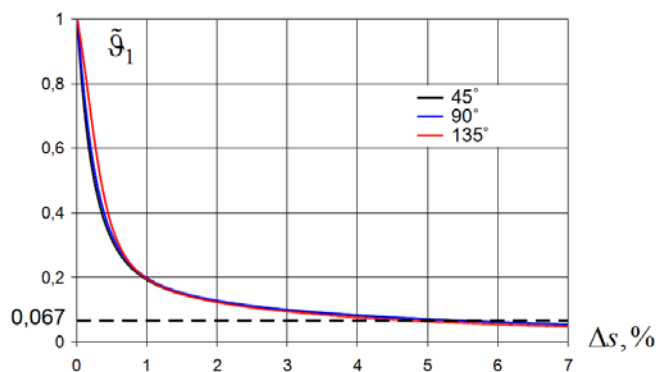


**Fig. 15.** Chart  $\tilde{\vartheta}_1 - \Delta s$  for different break angles of trajectories

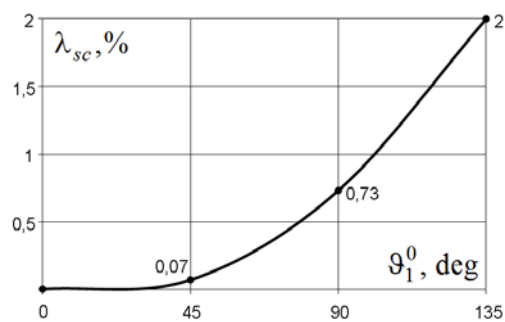


**Fig. 16.** Chart  $\lambda_{sc} - \vartheta_1^0$

To determine the effect of the length of the first link of the strain trajectory  $s_0$  on the scalar and vector properties of the material, numerical and experimental studies were conducted on the strain programs of testing are shown on Fig. 17. The specimens were subjected to the following strain history: specimens had been twisted to  $s_0 = \vartheta_3 = 1.5, 2, 2.5\%$ , and then stretched along the component  $\vartheta_1$  under constant  $\vartheta_3$ . The dependence  $\vartheta_1 - \Delta s$  characterizing vector characteristics of the material for model and experimental data is shown in Fig. 18.

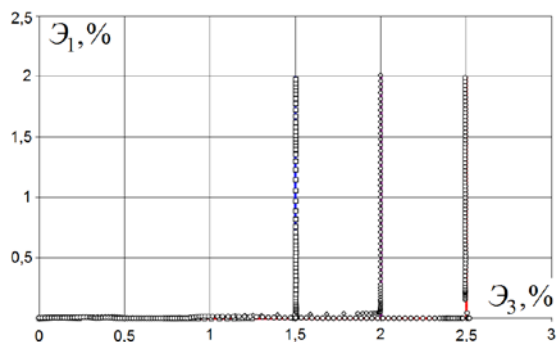

**Fig. 17.** Strain trajectories with different lengths of the first link

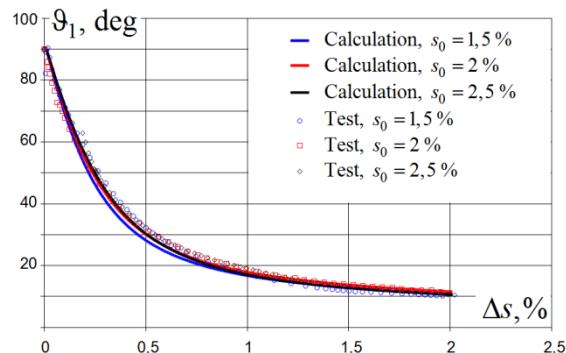

**Fig. 18.** Charts  $\vartheta_1 - \Delta s$

It is seen that the experimental points practically coincide with each other and are consistent with the numerical calculations of the proposed mathematical model. This means that the length of the first link of the strain trajectory, in the case of a simple (proportional) loading on it, practically does not affect the vector properties of the material and the value of the trace of delay  $\lambda$ . In case of replacing the trajectory to the break point by another section, for example, a circle, the trace of delay changes significantly [24].

## 5. Conclusion

The theoretical positions of the mathematical model of the theory of processes during deformation along two-link strain trajectories are verified in comparison with experimental data. Verification results indicate the correct modeling of elastoplastic deformation of structural steels for a given class of strain trajectories.

It is established that the trace of delay of vector properties and the trace of delay of the scalar characteristics of the material significantly depend on the break angle of the trajectories. This indicates the instability of the value of the trace of delay as a characteristic of the material.

**Acknowledgements.** No external funding was received for this study.

## References

- [1] Il'yushin AA. *Continuum Mechanics*. Moscow: MSU Publishing House; 1990. (In Russian)
- [2] Il'yushin AA. *Plasticity. Fundamentals of the General Mathematical Theory*. Moscow: Izd. Akad. Nauk SSSR; 1963. (In Russian)
- [3] Zubchaninov VG. *Mechanics of processes of plastic environments*. Moscow: Fizmatlit; 2010. (In Russian)
- [4] Zubchaninov VG. The General Mathematical Theory of Plasticity and the Il'yushin Postulates of Macroscopic Definability and Isotropy. *Moscow University Mechanics Bulletin*. 2018;73(5): 101–116.
- [5] Mitenkov FM, Volkov IA, Igumnov LA, Kaplienko AV, Korotkih YuG, Panov VA. *Applied theory of plasticity*. Moscow: Fizmatlit; 2015. (In Russian)
- [6] Annin BD, Zhigalkin VM. *Material Behavior under Conditions of Complex Loading*. Novosibirsk: Izdat. SO RAN; 1999. (In Russian)
- [7] Bondar VS. *Inelasticity. Variants of the theory*. New York: Begell House; 2013.
- [8] Peleshko V.A. Applied and engineering versions of the theory of elastoplastic processes of active complex loading part 2: Identification and verification. *Mechanics of Solids*. 2016;51(1): 91–113.
- [9] Krempl E, Lu H. The hardening and dependent behavior of fully annealed aisi type 304 stainless steel under biaxial in phase and out – of – phase strain cycling at room temperature. *ASME Journal of Engineering Materials and Technology*. 1984;106(4): 376-382.
- [10] Krieg R.D. A practical two surface plasticity theory. *Journal of Applied Mechanics*. 1975;42(3): 641-646.
- [11] Chaboche JL. A review of some plasticity and viscoplasticity theories. *International Journal of Plasticity*. 2008;24(10): 1642-1693.
- [12] Zubchaninov VG, Alekseev AA, Alekseeva EG, Gultiaev VI. Experimental verification of postulate of isotropy and mathematical modeling of elastoplastic deformation processes following the complex angled nonanalytic trajectories. *Materials Physics and Mechanics*. 2017;32(3): 298-304.
- [13] Zubchaninov VG, Alekseev AA, Alekseeva EG. Verification of the postulate of the isotropy and numerical simulation of the deformation of materials on a complex smooth trajectories. *Materials Physics and Mechanics*. 2016;29(2): 150-157. (In Russian)
- [14] Zubchaninov VG, Alekseev AA, Alekseeva EG. Mathematical modeling of plastic deformation of materials on complex flat trajectories. *Materials Physics and Mechanics*. 2015;24(2): 107-118. (In Russian)
- [15] Vasin RA. Some problems of the relationship between stresses and strains in multiaxial loading. *Elasticity and Inelasticity*. 1971;1: 59-126. (In Russian)
- [16] Kosarchuk VV, Koval'chuk BI. Formulation of the Law of Delay of the Vector Properties of Initially Anisotropic Materials. *Strength of Materials*. 1986;4(11): 1435-1439.
- [17] Zubchaninov VG, Alekseeva EG. Property of the delay a vector properties of materials for smooth path under complex loading. *Bulletin of the Yakovlev Chuvash State Pedagogical University. Series: Mechanics of Limit State*. 2014;2(20): 21-28. (In Russian)
- [18] Zubchaninov VG, Alekseeva EG. About influence of the curvature deformation path on

classification and delay of the properties of materials under complex loading. *Bulletin of the Yakovlev Chuvash State Pedagogical University. Series: Mechanics of Limit State*. 2014;1(19): 78-87. (In Russian)

[19] Zubchaninov VG, Alekseev AA, Gultiaev VI. Modeling of elastic-plastic deformation of work material along multielement piecewise zig-zag linear trajectories. *PNRPU Mechanics Bulletin*. 2017;3: 203-215.

[20] Korovin IM. Experimental determination of dependence tension deformation at difficult loading on a trajectory with one point break. *Engineering journal of Academy of Sciences of the USSR*. 1964;4: 592-600. (In Russian)

[21] Dao-Zuy-Bik. About a hypothesis of local definiteness in the plasticity theory. *Vestnik Moskovskogo Universiteta. Matematika, Mekhanika*. 1965;2: 67-75. (In Russian)

[22] Okhashi I, Tokuda N, Kurita I, Suzuki T. Certain experimental data on the Il'yushin general law of plasticity. *Izv. Akad. Nauk USSR, Mekh. Tverd. Tela*. 1981;6: 53-64.

[23] Lenskij VS. Experimental verification of the basic postulates of the general theory of elastoplastic deformations. In: *Questions of the theory of plasticity*. Izdatelstvo AN USSR; 1961. p. 58-82. (In Russian)

[24] Zubchaninov VG, Alekseeva EG. Delaying of vector and scalar properties of materials under complex loading. *Bulletin of the Yakovlev Chuvash State Pedagogical University. Series: Mechanics of Limit State*. 2012;4(14): 26-39. (In Russian)