

SURFACE TREATMENT OF NANO-STRUCTURED STEEL WITH PULSED LASER

Faezeh Mojtahedi^{1*}, Hamidreza Shahverdi^{1}, Mohammad Javad Torkamany^{2***}**

¹Material engineering department, Engineering faculty, Tarbiat modares university, Tehran, Iran

²Iranian National Center for Laser Science and Technology (INLC), Po Box:14665-576, Tehran, Iran

*e-mail: fa.mojtahedi@gmail.com

**e-mail: shahverdi@modares.ac.ir

***e-mail: mjtorkamany@yahoo.com

Abstract. In this paper, the laser surface treatment of $Fe_{52}Cr_{18}Mo_7B_{16}C_4Nb_3$ alloy has been investigated with the use of pulsed Nd:YAG laser, and the optimum pulse duration parameter for having finer microstructure, highest hardness and the most homogeneous surface has been studied. Melt profile and structure of laser processed samples were investigated by use of optical and field emission scanning electron microscopes and X-ray diffraction (XRD). Moreover, the mean crystallite size of laser treated zones was studied by the Scherrer formula. Hardness of the samples was measured by means of microhardness testing device. Results showed that by decreasing the laser pulse duration and power density in the surface of the laser treated zone the highest amount of the hardness can be achieved. Moreover, peak broadening phenomenon was observable in XRD patterns of samples with lower pulse duration. It is due to the increasing of thermal gradient in the surface as a result of decreasing power density.

1. Introduction

Over the past few years, the improvement of surface layers by different methods has attracted many investigators. Changing the microstructure contributes to many advantages such as corrosion, fatigue and wear resistance [1]. Surface melting and rapid solidification of surface layers by laser treatments can contribute to interesting properties and structures [2]. This technology allows us to convey large amount of energy in a very short time on the exact point of the surface [3]. It provides high power densities of 10^8 to 10^9 W/m² [4]. High energy laser beam can produce high rate unstable heat on the surface of bulk alloy and afford to fabrication of layers with appropriate properties and structures [5]. The cooling rates afforded by high power lasers are exactly in the bounds of the quench rates necessary for “amorphisation”, and therefore surface engineering by high power laser provides the chosen tool for this investigation into the fabrication of amorphous or nano-scale surface layers [6]. Depending on the thickness of the melt layer, a cooling rate in the order of 10^4 to 10^6 K/s can be achieved [7]. Because of precision of the process, short time and local effect of laser surface treatment, it can be also considered in precise industrial applications [8]. Fine crystalline materials obtained under the rapid cooling rate can exhibit high properties over micron-sized materials [1].

Laser surface treatment of steels [8, 9] and production of nano-crystalline structures on the surface of different alloys by laser beam have been investigated [2, 4, 6]. These layers exhibit attractive properties such as low friction, high hardness and good wear resistance [11].

3. Results and discussion

Variations of the melt pool depth of samples A1 to A3 are presented in Fig. 1. It is shown that by increasing the pulse duration, the depth of the processed zone increases. Hence, when the pulse duration increases, the volume of the processed area increases and it results to more depth of laser processed region. In addition, by increasing the pulse duration, the mean power of the processed area increases and contributes to more penetration of the melted zone. Exact amounts of penetration depths are shown in Fig. 2.

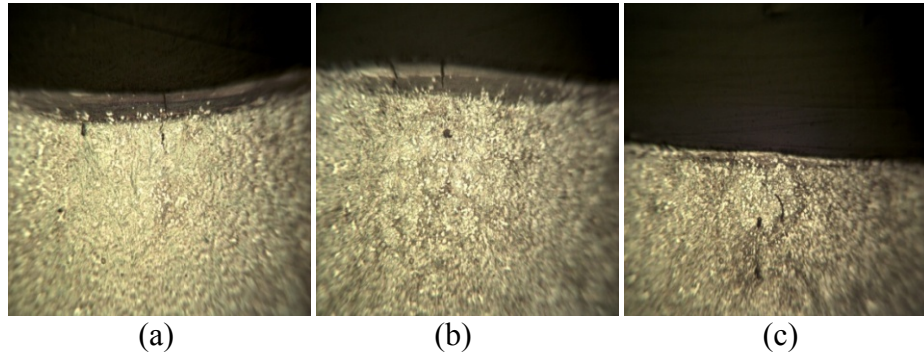


Fig. 1. Optical micrographs of samples A1 to A3.

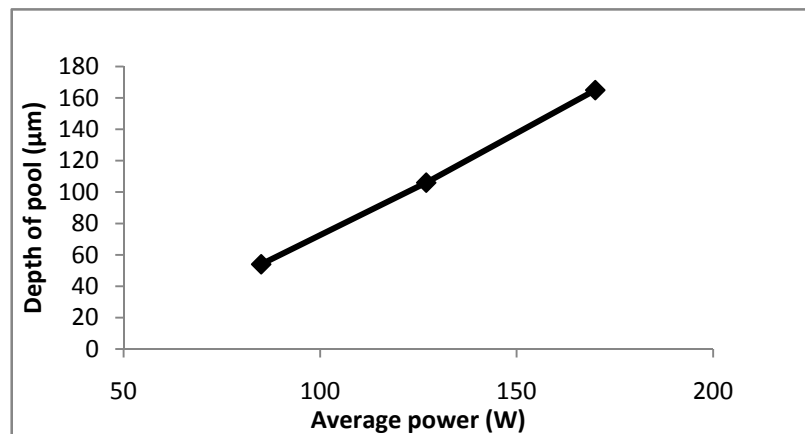


Fig. 2. Variation of the depth of the melt pool versus pulse average power.

Figure 3 shows the FESEM micrographs of the processed zone. It can be shown that by applying laser on the surface of the alloy, the microstructure becomes more uniform and tends to form a finer microstructure.

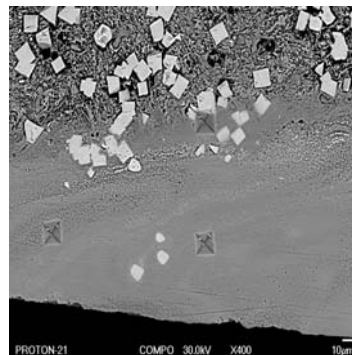


Fig. 3. FESEM micrograph of the processed zone.

It is due to the fact that applying laser on the surface contributes to high thermal gradient. Whereas the processed alloy tends to form glassy or nano-size microstructure with high thermal gradient, the processed zone has uniform and finer microstructure. As it can be seen, all the precipitations are solved in this area.

Figure 4 demonstrates the X-ray patterns of bulk alloy, samples A1 and A3. It shows that by applying laser on the surface of the alloy, some peaks that belong to some crystalline precipitation such as peaks of Cr_2C and Cr_2Nb disappear showing that the microstructure tends to become homogeneous. The main peak that belongs to $\alpha\text{-Fe}$ phase becomes wider, and signal to noise ratio decreases that overall means that the laser processed region tends to exhibit ultra-fine microstructure properties. Also, it is seen that by decreasing the average energy, the main peak becomes broader to somehow, and its FWHM improves. Also, some peaks that belong to Fe_2B or Fe_3B become wider. As it is explained in previous section, peak broadening is resulted from higher thermal gradient and finer microstructure. Crystallite sizes measured by the Scherrer formula confirm these pretensions. Table 3 shows the approximate amount of crystallite size on the surface of the alloy measured by the Scherrer formula. It demonstrates that by increasing the average energy, the crystallite size decreases.

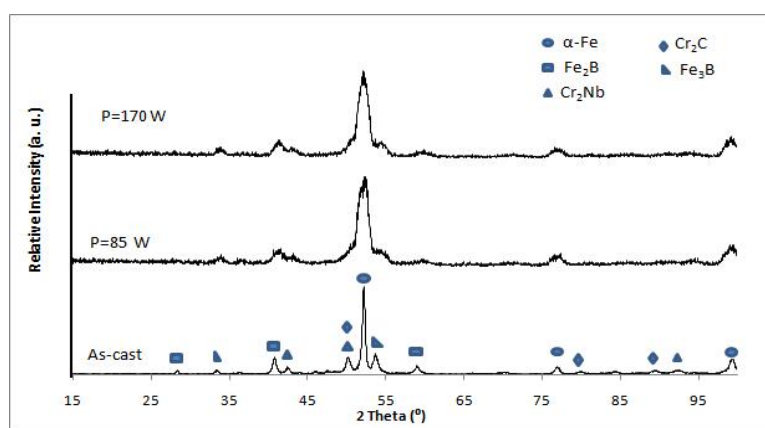


Fig. 4. XRD patterns of as-cast alloy, samples A1 and A3.

Table 3: Crystallite size of samples A1 and A3.

Sample	A1	A3
Mean crystallite size, nm	30	50

Figure 5 shows the average hardness of the surface of the samples. Since the microhardness of the as-cast alloy is about 600 HV, it is seen that laser processing will improve the surface microhardness.

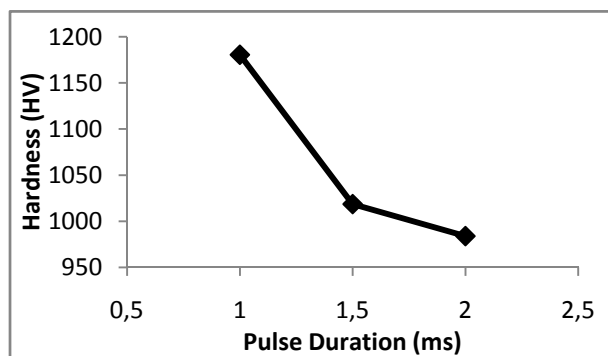


Fig. 5. Average hardness of all samples with different pulse durations.

It is shown that by increasing the pulse duration, the hardness of the treated surface decreases that is a direct result of the grain growth. As it is known, by increasing the pulse duration (in constant peak power) the average power increases and results to lower thermal gradient, so the microstructure becomes coarser. As a result wherever there is higher thermal gradient in the surface, microstructure becomes finer and contributes to higher hardness that occurs in lower pulse duration.

4. Conclusions

1. The uniformity of the microstructure improves by applying laser on the surface of the as-cast alloy.
2. By radiating lower pulse duration on the surface of the alloy, finer microstructure forms.
3. XRD analysis shows that lower pulse duration contributes to peak broadening, and it results to nano-scale microstructure.
4. By increasing the average energy, the hardness decreases, that is a direct result of grain growth.

Acknowledgments

The authors thank the Iranian National Center for Laser Science and Technology for technical support.

References

- [1] Ch. Cui, J. Hu, Y. Liu, K. Gao, Z. Guo // *Applied Surface Science* **254** (2008) 6779.
- [2] K.Y. Benyounis, O.M. Fakron, J.H. Abboud // *Materials and Design* **3** (2009) 674.
- [3] S. Kac, J. Kusinski // *Materials Chemistry and Physics* **81** (2003) 510.
- [4] Ch. Cui, J. Hu, Y. Liu, K. Gao, Z. Guo // *Applied Surface Science*. **254** (2008) 6779.
- [5] D.G. Morris // *Materials Science and Engineering* **97** (1988) 177.
- [6] D.T.A. Matthews, V. Ocelik, J.T.M. De Hosson // *Materials Science and Engineering A* **471** (2007) 155.
- [7] Y.H. Zhu, H.C. Man, W.B. Lee // *Journal of Materials Processing Technology* **139** (2003) 196.
- [8] B.S. Yilbas, S.Z. Shuja, S.M.A. Khan, A. Aleem // *Applied Surface Science* **255** (2009) 9396.
- [9] C.T. Kwok, F.T. Cheng, H.C. Man // *Surface and Coatings Technology* **202** (2007) 336.
- [10] J. Yang, J. Lian, Q. Dong, Z. Guo // *Applied Surface Science* **229** (2004) 2.
- [11] D.T.A. Matthews, V. Ocelik, D. Branagan, J.T.M. De Hosson // *Surface and Coatings Technology* **23(13)** (2009) 1833.
- [12] E. Gualtieri, A. Borgh, L. Calabri, N. Pugno, S. Valeri // *Tribology International* **42** (2009) 699.
- [13] S.P. Harimkar, S.R. Paital, A. Singah, R. Aalund, N.B. Dahotre // *Journal of Non-Crystalline Solids* **355** (2009) 2179.
- [14] Q. Chen, D. Zhang, J. Shen, H. Fan, J. Sun // *Journal of Alloys and Compounds* **427** (2007) 190.
- [15] A. Basu, A.N. Samant, S.P. Harimkar, J. Dutta Majumdar, I. Manna, N.B. Dahotre // *Surface and Coatings Technology* **202** (2008) 2623.
- [16] B. Mahmoudi, M.J. Torkamany, A.R. Sabour Rouh Aghdam, J. Sabbaghzade // *Materials and Design* **31** (2010) 2553.
- [17] M.J. Torkamany, M.J. Hamedi, F. Malek, J. Sabbaghzadeh // *Journal of Physics D: Applied Physics* **39** (2006) 4563.